

LIEN A Co., Ltd.  
55/1A Khuong Viet Street Phu Trung Ward, Tan Phu District  
Ho Chi Minh City  
Vietnam

## Test Report No. 59327-A001-A002-L

Test objective:	Analysis according to eco- <b>INSTITUT</b> -Label-criteria
Article designation according to order:	A001: Natural Latex A002: C. Fusion Latex
Date of report:	13/08/2024
Number of pages of report:	29
Testing / responsible laboratory:	eco- <b>INSTITUT</b> Germany GmbH, Köln
Note:	The test results in the report refer exclusively to the submitted test sample. The report may only be used in product and company advertising if a valid certificate is available that refers to this report. More information at <a href="http://www.eco-institut.de/en/advertising">www.eco-institut.de/en/advertising</a>



## Content

Sample View.....	3
Laboratory report.....	4
1 Emission analysis.....	4
1.1 Sample A001, Volatile organic compounds after 2 days.....	5
1.2 Sample A001, Volatile organic compounds after 7 days.....	9
1.3 Carbon disulfide (CS <sub>2</sub> , test chamber).....	13
1.4 Ammonia (test chamber).....	14
1.5 Nitrosamines (test chamber) †#.....	15
2 Odour Testing .....	16
3 Polymer content # .....	17
4 Ash content # .....	18
5 Organic halogenated compounds (AOX / EOX) †#.....	19
6 Polycyclic aromatic hydrocarbons (PAH) †# .....	20
7 Aniline †# .....	21
Appendix.....	22
Sampling sheet.....	22
List of calibrated Volatile Organic Compounds (VOC).....	24
Definition of terms.....	26
Commentary on emission analysis.....	28
Explanation of Specific Emission Rate SER.....	29

---

† subcontracted, # outside accreditation

## Sample View


### Internal sample number (filled in by laboratory)

Photo of the test specimen: A001

Article designation according to order:  
Sample/batch number according to order:  
Type of sample:  
Date of production:  
Sampling by:  
Date of sampling:  
Location of sampling:

Receipt of sample / Condition upon delivery:

59327-A001

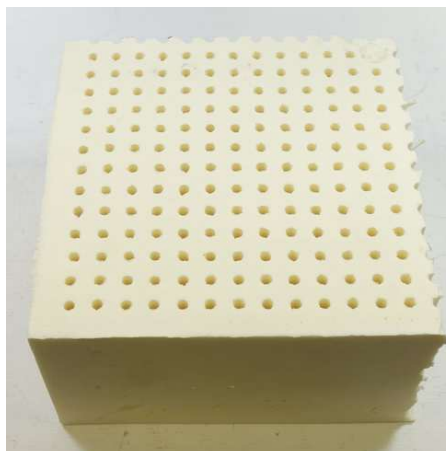

Natural Latex  
100701006017  
Mattress core  
01/07/2024  
Le Huu Nghi, International Environment Co.Ltd  
03/07/2024  
35/10, 48 Street, 14 Ward, Go Vap District, Ho Chi Minh City,  
Vietnam  
08/07/2024 / without objection

### Internal sample number (filled in by laboratory)

Photo of the test specimen: A002

Article designation according to order:  
Sample/batch number according to order:  
Type of sample:  
Date of production:  
Sampling by:  
Date of sampling:  
Location of sampling:

Receipt of sample / Condition upon delivery:

59327-A002



C. Fusion Latex  
10070155  
Pillow  
01/07/2024  
Le Huu Nghi, International Environment Co.Ltd  
03/07/2024  
35/10, 48 Street, 14 Ward, Go Vap District, Ho Chi Minh City,  
Vietnam  
08/07/2024 / without objection

# Laboratory report

## 1 Emission analysis

### Test method

DIN EN 16516:2020-10 | Testing and evaluation of the release of dangerous substances;  
determination of emissions into indoor air

### A001, Preparation of test specimen

Date: 23/07/2024  
Test specimen preparation: Sample cut to size; transfer of the test specimen into the test chamber immediately after preparation  
Masking of backside: no  
Masking of edges: no  
Relationship of unmasked edges to surface: not applicable  
Loading reference unit: area-specific [m<sup>2</sup>]  
Dimensions: 27.7 cm x 27.7 cm x 15.5 cm

### A001, Test chamber conditions according to DIN EN ISO 16000-9:2008-04

Chamber volume: 0.250 m<sup>3</sup>  
Temperature: 23 °C ± 1 °C  
Relative humidity: 50 % ± 1 %  
Air pressure: normal  
Air: cleaned  
Air change rate: 0.5 h<sup>-1</sup>  
Air velocity: 0.3 m/s  
Loading: 0.65 m<sup>2</sup>/m<sup>3</sup>  
Specific air flow rate: 0.769 m<sup>3</sup>/(m<sup>2</sup>·h)  
Starting time of the test (t<sub>0</sub>): 23/07/2024  
Air sampling: 2 days after test chamber loading  
7 days after test chamber loading

### Analytcs

Aldehydes and ketones: DIN ISO 16000-3:2023-12  
Limit of quantification: 2 µg/m<sup>3</sup>  
Volatile organic compounds: DIN ISO 16000-6:2022-03  
Limit of quantification: 1 µg/m<sup>3</sup> (1,4-Cyclohexanedimethanol, Diethylene glycol,  
1,4-Butanediol: 5 µg/m<sup>3</sup>)  
Note for analysis: not specified

## 1.1 Sample A001, Volatile organic compounds after 2 days

### Test objective:

Volatile organic compounds (VOC), test chamber, air sampling 2 days after test chamber loading

### Test result:

Internal sample number: | 59327-A001

	Substance	CAS No.	RT [min]	Concentration+ calib. substances ≥ 1 µg/m³ uncalib. substances ≥ 1 µg/m³ DNPH ≥ 2 µg/m³ [µg/m³]	Toluene- equivalent substances ≥ 5 µg/m³ [µg/m³]	SER+ [µg/(m²·h)]	CMR Classifi- cation++	LCI AgBB 2021 [µg/m³]	R-value
	<b>Aromatic hydrocarbons</b>								
VOC	Toluene	108-88-3	8.26	8	8	6.2	Repr. 2	2900	0.00
VOC	1-Isopropyl-4-methylbenzene (p-Cymene)	99-87-6	14.23	2	< 5	1.5		1000	0.00
	<b>Aliphatic hydrocarbons (n-, iso- and cyclo-)</b>								
VOC	Methylcyclohexane	108-87-2	7.40	1	< 5	0.77		8100	0.00
	<b>Terpenes</b>								
VOC	Limonene	138-86-3	14.37	3	< 5	2.3		5000	0.00
	<b>Aliphatic mono alcohols (n-, iso-, cyclo-) and dialcohols</b>								
VOC	1-Butanol	71-36-3	5.86	2	< 5	1.5		3000	0.00
VOC	2-Ethyl-1-hexanol	104-76-7	13.99	2	< 5	1.5		300	0.01
	<b>Glycols, Glycol ethers, Glycol esters</b>								
VOC	Ethylene glycol (Ethane-1,2- diol)	107-21-1	6.28	2	< 5	1.5		3400	0.00
	<b>Aldehydes</b>								
VOC	Pentanal (Valeraldehyde)	110-62-3	6.58	2	< 5	1.5		800	0.00
VOC	Hexanal	66-25-1	8.78	15	8	12		900	0.02
VOC	Nonanal	124-19-6	15.70	5	5	3.8		900	0.01
VOC	Benzaldehyde	100-52-7	12.87	2	< 5	1.5		90	0.02
VVOC	Acetaldehyde	75-07-0		3	n. d.	2.3	Carc. 1B Muta. 2	300	0.01
VVOC	Formaldehyde	50-00-0		2	n. d.	1.5	Carc. 1B Muta. 2	100	0.02



	Substance	CAS No.	RT [min]	Concentration+ calib. substances ≥ 1 µg/m³ uncalib. substances ≥ 1 µg/m³ DNPH ≥ 2 µg/m³ [µg/m³]	Toluene- equivalent substances ≥ 5 µg/m³ [µg/m³]	SER+ [µg/(m²·h)]	CMR Classifi- cation++	LCI AgBB 2021 [µg/m³]	R-value
	<b>Esters</b>								
VOC	n-Butyl acetate	123-86-4	8.98	3	< 5	2.3		4800	0.00
VOC	n-Butyl acrylate	141-32-2	10.91	9	6	6.9	Group 3	110	0.08
	<b>Other identified substances in addition to LCI list</b>								
VOC	Benzothiazole	95-16-9	19.19	5	5	3.8			
VOC	2,2,4,6,6-Pentamethylheptane	13475-82-6	13.37	13	18	10		6000	0.00
VVOC	probably diethylamine m/z 58 44 73*		4.50	14	14	11			
VOC	probably butyl ether m/z 57 41 87*		10.64	10	10	7.7			
VOC	Ester m/z 57 75 87*		11.15	3	< 5	2.3			
VOC	Ester m/z 71 89 56*		13.18	2	< 5	1.5			
VOC	Other saturated aliphatic hydrocarbons C9 - C16*	--	13.71	2	< 5	1.5		6000	0.00
VOC	Other terpenes*	--	14.94	3	< 5	2.3		1400	0.00
VOC	m/z 133 105 148*		15.51	2	< 5	1.5			
VOC	several not ident. substances*		15.8-18.4	8	8	6.2			
VOC	m/z 57 97 112*		19.40	7	7	5.4			
VOC	m/z 59 97 83*		20.95	11	11	8.5			
VOC	several not ident. substances*		21.06-21.5	10	10	7.7			

+ identified and calibrated substances, substance specific calculated

++ classification according to Regulation (EG) N° 1272/2008: Categories Carc. 1A, 1B and 2, Muta. 1A, 1B and 2, Repr. 1A, 1B and 2, TRGS 905: K1A, K1B, K2, M1A, M1B, M2, R1A, R1B, R2; IARC: Group 1, 2A, 2B and 3, DFG MAK-list: Kategorie III1 to III5

\* unidentified substances, calculated as toluene equivalent reported with significant mass fragments as mass-to-charge ratio (m/z)

n. d.: not determined



<b>Carcinogenic, mutagenic, and reproductive toxic compounds*</b>	<b>Concentration after 2 days [µg/m³]</b>	<b>SERa [µg/(m² · h)]</b>
CMR 1: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EC) No. 1272/2008: Category Carc. 1A and 1B, Muta. 1A and 1B, Repr. 1A and 1B; TRGS 905: K1A, K1B, M1A, M1B, R1A, R1B; IARC: Group 1 and 2A; DFG (MAK list): Categories III1, III2 (sum)	<b>&lt; 1</b>	<b>&lt; 0.77</b>
C 1: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EG) Nr. 1272/2008: Category Carc. 1A u. 1B; TRGS 905: K1A, K1B (sum)	<b>&lt; 1</b>	<b>&lt; 0.77</b>

<b>TVOC, Total volatile organic compounds</b>	<b>Concentration after 2 days [µg/m³]</b>	<b>SERa [µg/(m² · h)]</b>
Sum of VOC according to DIN EN 16516	<b>96</b>	<b>74</b>
Sum of VOC according to AgBB 2021	<b>100</b>	<b>78</b>
Sum of VOC according to eco-INSTITUT-Label	<b>130</b>	<b>100</b>
Sum of VOC according to DIN ISO 16000-6	<b>190</b>	<b>150</b>

<b>TSVOC, Total semi volatile organic compounds</b>	<b>Concentration after 2 days [µg/m³]</b>	<b>SERa [µg/(m² · h)]</b>
Sum of SVOC according to DIN EN 16516	<b>&lt; 5</b>	<b>&lt; 3.8</b>
Sum of SVOC without LCI according to AgBB 2021	<b>&lt; 5</b>	<b>&lt; 3.8</b>
Sum of SVOC without LCI according to eco-INSTITUT-Label	<b>&lt; 1</b>	<b>&lt; 0.77</b>
Sum of SVOC with LCI according to AgBB 2021	<b>&lt; 5</b>	<b>&lt; 3.8</b>

<b>TVVOC, Total very volatile organic compounds</b>	<b>Concentration after 2 days [µg/m³]</b>	<b>SERa [µg/(m² · h)]</b>
Sum of VVOC according to AgBB 2021	<b>14</b>	<b>11</b>
Sum of VVOC according to eco-INSTITUT-Label	<b>19</b>	<b>15</b>

\*Excluding formaldehyde and acetaldehyde (Carc. 1B) due to an assumed "practical threshold" under which a significant carcinogenic risk is no longer to be expected (see Federal Institute for Risk Assessment (2006): Toxicological evaluation of formaldehyde and Federal Environment Agency (2016): Reference value for formaldehyde in indoor air and protocol of the 11th meeting of 'Ausschusses für Innenraumrichtwerte' (AIR), 11/2020). In the case of a toxicological emission assessment, a single-substance analysis of the concentrations is necessary. In the opinion of the committee for Indoor Air Guide Values (Ausschuss für Innenraumrichtwerte) of the Federal Environment Agency, the concentration of 0.1 mg formaldehyde/m³ indoor air, based on a measurement period of half an hour, should not be exceeded, also for a short time (Bundesgesundheitsblatt 2016 · 59: 1040-1044 DOI 10.1007 / s00103 -016-2389-5 © Springer-Verlag Berlin Heidelberg 2016).



Other sums of VOC	Concentration after 2 days [µg/m³]	SERa [µg/(m² · h)]
VOC without LCI according to AgBB 2021 (sum)	51	39
VOC without LCI according to eco-INSTITUT-Label (sum)	58	45
CMR 2: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EC) No. 1272/2008: Category Carc. 2, Muta. 2, Repr. 2; TRGS 905: K2, M2, R2; IARC: Group 2B; DFG (MAK list): Category III3 (sum)	13	10
Sensitising compounds with the following categorisations: DFG (MAK list): Category IV; Regulation (EC) No. 1272/2008: skin sensitising, respiratory sensitising; TRGS 907 (sum)	16	12
Bicyclic Terpenes (sum)	< 1	< 0.77
C9 - C14 Alkanes / Isoalkanes as dekane-equivalent (sum)	13	10
C4 - C11 Aldehydes, acyclic, aliphatic (sum)	22	17
C9 - C15 Alkylated benzenes (sum)	2	1.5
Kresoles (sum)	< 1	< 0.77

Risk value for assessment of LCI	R-value
R-value according to eco-INSTITUT-Label	0.18
R-value according to AgBB 2021	0.11
R-value according to Belgian regulation	0.11
R-value according to EU-LCI	0.11

Note:

Due to different requirements in the respective guidelines, the calculation of TVOC, TVVOC, TSVOC and R-value may result in different values. Short-chain carbonyl compounds (C1-C5) are quantified via HPLC acc. to DIN ISO 16000-3:2013-01. Therefore, no toluene equivalents are given for VVOC. These substances are taken into concern by means of their substance specific calibration via the sum of VVOC acc. to DIN EN 16516:2020-10. For VOC however, the substance specific calibration takes place via HPLC whereas the TVOC is calculated using the toluene equivalent determined via Tenax acc. to DIN EN 16516:2020-10.



## 1.2 Sample A001, Volatile organic compounds after 7 days

### Test objective:

Volatile organic compounds (VOC), test chamber, air sampling 7 days after test chamber loading

### Test result:

Internal sample number: | 59327-A001

	Substance	CAS No.	RT [min]	Concentration+ calib. substances ≥ 1 µg/m³ uncalib. substances ≥ 1 µg/m³ DNPH ≥ 2 µg/m³ [µg/m³]	Toluene- equivalent substances ≥ 5 µg/m³ [µg/m³]	SER+ [µg/(m²·h)]	CMR Classifi- cation++	LCI AgBB 2021 [µg/m³]	R-value
	<b>Aromatic hydrocarbons</b>								
VOC	1-Isopropyl-4-methylbenzene (p-Cymene)	99-87-6	14.06	2	< 5	1.5		1000	0.00
	<b>Terpenes</b>								
VOC	Limonene	138-86-3	14.20	2	< 5	1.5		5000	0.00
	<b>Aliphatic mono alcohols (n-, iso-, cyclo-) and dialcohols</b>								
VOC	2-Ethyl-1-hexanol	104-76-7	13.84	1	< 5	0.77		300	0.00
	<b>Aromatic alcohols</b>								
VOC	2,6-Di-tert-butyl-4- methylphenol (BHT)	128-37-0	24.11	1	< 5	0.77	Group 3	100	0.01
	<b>Aldehydes</b>								
VOC	Pentanal (Valeraldehyde)	110-62-3	6.66	1	< 5	0.77		800	0.00
VOC	Hexanal	66-25-1	8.74	3	< 5	2.3		900	0.00
VOC	Nonanal	124-19-6	15.53	4	< 5	3.1		900	0.00
VOC	Benzaldehyde	100-52-7	12.74	2	< 5	1.5		90	0.02
VVOC	Acetaldehyde	75-07-0		2	n. d.	1.5	Carc. 1B Muta. 2	300	0.01
VVOC	Formaldehyde	50-00-0		2	n. d.	1.5	Carc. 1B Muta. 2	100	0.02
	<b>Esters</b>								
VOC	n-Butyl acrylate	141-32-2	10.80	2	< 5	1.5	Group 3	110	0.02
	<b>Other identified substances in addition to LCI list</b>								
VOC	Benzothiazole	95-16-9	18.99	5	< 5	3.8			
VOC	2,2,4,6,6-Pentamethylheptane	13475-82-6	13.19	7	9	5.4		6000	0.00



	Substance	CAS No.	RT	Concentration+ calib. substances ≥ 1 µg/m³ uncalib. substances ≥ 1 µg/m³ DNPH ≥ 2 µg/m³	Toluene- equivalent substances ≥ 5 µg/m³	SER+	CMR Classifi- cation++	LCI AgBB 2021	R-value
			[min]	[µg/m³]	[µg/m³]	[µg/(m²·h)]		[µg/m³]	
VOC	probably diethylamine m/z 58 44 73*		4.50	5	5	3.8			
VOC	probably butyl ether m/z 57 41 87*		10.64	2	< 5	1.5			
VOC	Ester m/z 57 75 87*		11.15	1	< 5	0.77			
VOC	Ester m/z 71 89 56*		13.18	1	< 5	0.77			
VOC	several not ident. substances*		15.8- 18.4	5	5	3.8			
VOC	m/z 57 97 112*		19.40	4	< 5	3.1			
VOC	m/z 59 97 83*		20.95	10	10	7.7			
VOC	several not ident. substances*		21.06- 21.5	10	10	7.7			

+ identified and calibrated substances, substance specific calculated

++ classification according to Regulation (EG) N° 1272/2008: Categories Carc. 1A, 1B and 2, Muta. 1A, 1B and 2, Repr. 1A, 1B and 2, TRGS 905: K1A, K1B, K2, M1A, M1B, M2, R1A, R1B, R2; IARC: Group 1, 2A, 2B and 3, DFG MAK-list: Kategorie III1 to III5

\* unidentified substances, calculated as toluene equivalent reported with significant mass fragments as mass-to-charge ratio (m/z)

n. d.: not determined



<b>Carcinogenic, mutagenic, and reproductive toxic compounds*</b>	<b>Concentration after 7 days [µg/m³]</b>	<b>SERa [µg/(m² · h)]</b>
CMR 1: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EC) No. 1272/2008: Category Carc. 1A and 1B, Muta. 1A and 1B, Repr. 1A and 1B; TRGS 905: K1A, K1B, M1A, M1B, R1A, R1B; IARC: Group 1 and 2A; DFG (MAK list): Categories III1, III2 (sum)	< 1	< 0.77
C 1: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EG) Nr. 1272/2008: Category Carc. 1A u. 1B; TRGS 905: K1A, K1B (sum)	< 1	< 0.77

<b>TVOC, Total volatile organic compounds</b>	<b>Concentration after 7 days [µg/m³]</b>	<b>SERa [µg/(m² · h)]</b>
Sum of VOC according to DIN EN 16516	34	26
Sum of VOC according to AgBB 2021	32	25
Sum of VOC according to eco-INSTITUT-Label	63	48
Sum of VOC according to DIN ISO 16000-6	110	85

<b>TSVOC, Total semi volatile organic compounds</b>	<b>Concentration after 7 days [µg/m³]</b>	<b>SERa [µg/(m² · h)]</b>
Sum of SVOC according to DIN EN 16516	< 5	< 3.8
Sum of SVOC without LCI according to AgBB 2021	< 5	< 3.8
Sum of SVOC without LCI according to eco-INSTITUT-Label	< 1	< 0.77
Sum of SVOC with LCI according to AgBB 2021	< 5	< 3.8

<b>TVVOC, Total very volatile organic compounds</b>	<b>Concentration after 7 days [µg/m³]</b>	<b>SERa [µg/(m² · h)]</b>
Sum of VVOC according to AgBB 2021	5	3.8
Sum of VVOC according to eco-INSTITUT-Label	9	6.9

\*Excluding formaldehyde and acetaldehyde (Carc. 1B) due to an assumed "practical threshold" under which a significant carcinogenic risk is no longer to be expected (see Federal Institute for Risk Assessment (2006): Toxicological evaluation of formaldehyde and Federal Environment Agency (2016): Reference value for formaldehyde in indoor air and protocol of the 11th meeting of 'Ausschusses für Innenraumrichtwerte' (AIR), 11/2020). In the case of a toxicological emission assessment, a single-substance analysis of the concentrations is necessary. In the opinion of the committee for Indoor Air Guide Values (Ausschuss für Innenraumrichtwerte) of the Federal Environment Agency, the concentration of 0.1 mg formaldehyde/m³ indoor air, based on a measurement period of half an hour, should not be exceeded, also for a short time (Bundesgesundheitsblatt 2016 · 59: 1040-1044 DOI 10.1007 / s00103 -016-2389-5 © Springer-Verlag Berlin Heidelberg 2016).



Other sums of VOC	Concentration after 7 days [µg/m³]	SERa [µg/(m² · h)]
VOC without LCI according to AgBB 2021 (sum)	25	19
VOC without LCI according to eco-INSTITUT-Label (sum)	38	29
CMR 2: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EC) No. 1272/2008: Category Carc. 2, Muta. 2, Repr. 2; TRGS 905: K2, M2, R2; IARC: Group 2B; DFG (MAK list): Category III3 (sum)	4	3.1
Sensitising compounds with the following categorisations: DFG (MAK list): Category IV; Regulation (EC) No. 1272/2008: skin sensitising, respiratory sensitising; TRGS 907 (sum)	7	5.4
Bicyclic Terpenes (sum)	< 1	< 0.77
C9 - C14 Alkanes / Isoalkanes as dekane-equivalent (sum)	7	5.4
C4 - C11 Aldehydes, acyclic, aliphatic (sum)	8	6.2
C9 - C15 Alkylated benzenes (sum)	2	1.5
Cresols (sum)	< 1	< 0.77

Risk value for assessment of LCI	R-value
R-value according to eco-INSTITUT-Label	0.09
R-value according to AgBB 2021	0.00
R-value according to Belgian regulation	0.00
R-value according to EU-LCI	0.00

Note:

Due to different requirements in the respective guidelines, the calculation of TVOC, TVVOC, TSVOC and R-value may result in different values. Short-chain carbonyl compounds (C1-C5) are quantified via HPLC acc. to DIN ISO 16000-3:2013-01. Therefore, no toluene equivalents are given for VVOC. These substances are taken into concern by means of their substance specific calibration via the sum of VVOC acc. to DIN EN 16516:2020-10. For VOC however, the substance specific calibration takes place via HPLC whereas the TVOC is calculated using the toluene equivalent determined via Tenax acc. to DIN EN 16516:2020-10.



### 1.3 Carbon disulfide (CS<sub>2</sub>, test chamber)

**Test parameter:**

Carbon disulfide (CS<sub>2</sub>)

**Test method:**

Analytics: | DIN ISO 16000-6:2022-03

**Test result:**

Internal Sample number	Measurement time (after test chamber loading)	Concentration (test chamber) [µg/m <sup>3</sup> ]	Limit of quantification [µg/m <sup>3</sup> ]
59327-A001	2 days	1	1



## 1.4 Ammonia (test chamber)

**Test parameter:**

Ammonia, test chamber

**Test method:**

Method description / Analytics: Sampling from test chamber air according to DIN EN 16516:2020-10 using silica gel tubes with sulfuric acid coating.  
Determination of the ammonia concentration via UV/VIS spectroscopic determination of the indophenol concentration formed by the Berthelot reaction (analogous to ISO 7150-1:1984).

Limit of quantification: 10 µg/m<sup>3</sup>

**Test result:**

Internal sample number	Measurement time (after test chamber loading)	Concentration (Test chamber air) [µg/m <sup>3</sup> ]	Specific Emission Rate (SER) [µg/(m <sup>2</sup> ·h)]
59327-A001	7 days	130	100

## 1.5 Nitrosamines (test chamber) ‡#

### Test parameter:

Determination of Nitrosamines

### Test method:

Method description / analytics: | IFA 8172 (IV/18) resp. DGUV-Information 213-523 (09/2019)

### Test result:

Internal sample number	Parameter	Measurement time (after test chamber loading)	Concentration (test chamber air) [ng/m <sup>3</sup> ]	limit of quantification [ng/m <sup>3</sup> ]
59327-A001	N-Nitrosodimethylamine (NDMA)	2 days	< LOQ	20
	N-Nitrosomethylethylamine (NMEA)		< LOQ	20
	N-Nitrosodiethylamine (NDEA)		51	20
	N-Nitrosodiisopropylamine (NDIPA)		< LOQ	20
	N-Nitrosodiisobutylamine (NDIBA)		< LOQ	20
	N-Nitrosodipropylamine (NDPA)		< LOQ	20
	N-Nitrosodibutylamine (NDBA)		< LOQ	20
	N-Nitrosopyrrolidine (NPYR)		< LOQ	20
	N-Nitrosopiperidine (NPIP)		< LOQ	20
	N-Nitrosomorpholine (NMOR)		< LOQ	20

< LOQ = Value below limit of quantification

Remark: Concentrations below the limit of quantification are between limit of detection and limit of quantification and provide only qualitative evidence.



## 2 Odour Testing

**Test parameter:**

Assessment of odour emissions

**Test Method:**

Analytics: Determination of odour as part of the eco-INSTITUT-Label-Certification, house method (following VDA recommendation 270:2018)

**Test result:**

Internal sample number: 59327-A001

**Test conditions**

Test chamber	see 1 Emission analysis
Air sampling [days]	2
Probands	5
Therefrom female	2
Evaluation Acceptance	Continuous scale from +1 (not perceptible) to +6 (unbearable)

	Evaluation
Odour intensity after 2 days (arithmetic mean)	2.7

**Individual results:**

Test person	Odour after 2 days [Note]
Test person 01	2.5
Test person 02	2.0
Test person 03	3.0
Test person 04	3.0
Test person 05	3.0



### 3 Polymer content #

**Test parameter:**

Relation between natural rubber (NR) and synthetic rubber (SBR)

**Test method:**

Method description / Analytics: | IR/ATR

**Test result:**

Internal sample number	Polymer content	[weight/%]
59327-A002	NR, with reference to the polymer content <sup>1) 2) 3)</sup>	100
	SBR, with reference to the polymer content	0

<sup>1)</sup> The relative expanded measurement uncertainty (k=2) for the content of NR is 21.6 %.

<sup>2)</sup> If NR content is < 5 %, the result is shown as 100 % SBR. Usually there is no use of NR below 5 % in a mixture of NR and SBR.

<sup>3)</sup> The content of NR is based on the assumption that polyisoprene in latex mattresses is always of natural origin.

## 4 Ash content #

### Test parameter:

Ash content, filler content

### Test method:

Analytically: Thermogravimetry at 900 °C  
Reproducibility of the analytical balance: 0.2 mg

### Test result:

Internal sample number: 59327-A002

Duplicate Determination	Applied sample amount	Mass of the porcelain crucible	Mass porcelain crucible + sample after heating	Mass ash	Ash content	Filler content
	[g]	[g]	[g]	[g]	[%]	[%]
Determination 1	1.1173	43.1668	43.2823	0.1155	10.3	5.3
Determination 2	1.2022	40.2915	40.4170	0.1255	10.4	5.4

Parameter	Content [M%]
Ash content (incl. zinc oxide), with reference to the sample	10.4
Filler content, with reference to the sample <sup>1)</sup>	5.4

<sup>1)</sup> The amount of filler is calculated as difference between the amount of ash and zinc oxide, assuming that the maximum of zinc oxide is 5 % of the total latex foam.

## 5 Organic halogenated compounds (AOX / EOX) ‡#

### Test parameter:

Determination of adsorbable organohalogen compounds (AOX) and extractable organohalogen compounds (EOX) from the material.

### Test method:

Method description:

AOX determination from hot water extracts of solid materials (P 504-408).  
EOX determination in solid materials (P 504-409).

Analytics:

AOX: DIN EN ISO 9562:2005-02, calculated as chlorine.  
EOX: DIN 38414-17:2017-01, calculated as chlorine.

### Test result:

Internal sample number	Parameter	Content (Material) [mg/kg]	Limit of quantification [mg/kg]
59327-A002	AOX	< LOQ	0.5
	EOX	< LOQ	2

< LOQ = Value below limit of quantification

## 6 Polycyclic aromatic hydrocarbons (PAH) ‡#

### Test parameter:

Polycyclic aromatic hydrocarbons (PAH)

### Test method:

Method description / Analytics: | AfPS GS 2019:01 PAH

### Test result:

Internal sample number	Parameter	CMR-Classification*	Content (Material) [mg/kg]	Limit of quantification [mg/kg]
59327-A002	Naphthalene	Carc. 2	< LOQ	0.5
	Acenaphthylene	-	< LOQ	0.2
	Acenaphthene	-	< LOQ	0.2
	Fluorene	-	< LOQ	0.2
	Phenanthrene	-	< LOQ	0.2
	Anthracene	-	< LOQ	0.2
	Fluoranthene	-	< LOQ	0.2
	Pyrene	-	< LOQ	0.2
	Benzo(a)anthracene	Carc. 1B	< LOQ	0.2
	Chrysene	Carc. 1B, Muta. 2	< LOQ	0.2
	Benzo(b)fluoranthene	Carc. 1B	< LOQ	0.2
	Benzo(j)fluoranthene	Carc. 1B	< LOQ	0.2
	Benzo(k)fluoranthene	Carc. 1B	< LOQ	0.2
	Benzo(a)pyrene	Carc. 1B, Muta. 1B, Repr. 1B	< LOQ	0.2
	Benzo(e)pyrene	Carc. 1B	< LOQ	0.2
	Indeno(1,2,3-cd)pyrene	-	< LOQ	0.2
	Dibenz(a,h)anthracene	Carc. 1B	< LOQ	0.2
	Benzo(g,h,i)perylene	-	< LOQ	0.2
Sum PAH		< LOQ		

\*Classification according to Regulation (EG) N° 1272/2008

< LOQ = Value below limit of quantification

## 7 Aniline ‡#

### Test parameter:

Determination of the aniline content in material samples

### Test method:

Method description / Analytics:

LA-LC-103.01\_28.05.2014  
- extraction  
- analysis by LC-MS/MS  
Aniline is an unvalidated parameter.

### Test result:

Internal sample number	Content (Material) [mg/kg]	Limit of quantification [mg/kg]
59327-A001	0.34	0.1

Cologne, 13/08/2024



Michael Stein, Dipl.-Chem.  
(Laboratory Management)



# Appendix

## Sampling sheet



### Sampling Sheet

Please fill in all fields. If the fields marked \* are not filled in, the test piece cannot be accepted for laboratory testing.

# 59327-001

Please take one sampling sheet for each sample! The sampling instruction must be strictly maintained!

<p><b>Order by*</b></p> <p><input checked="" type="checkbox"/> <b>Name of production company</b> Lien A Co., Ltd. 55/1A Khuong Viet Street, Phu Trung Ward, Tan Phu District, Ho Chi Minh City, Vietnam</p> <p><b>Name of distribution</b> (if different from production)</p> <p><b>Name of test sample/ item*</b> Natural Latex</p> <p><b>Article number</b></p> <p><b>Model / Program / Series</b> Pincore</p> <p><b>Sample taken from</b> <input checked="" type="checkbox"/> current production <input type="checkbox"/> storage <input type="checkbox"/> other</p> <p><b>Storage location</b></p>	<p><b>Testing laboratory</b> eco-INSTITUT Germany GmbH Schanzenstr. 6-20, Carlswerk 1.19 D - 51063 Köln Tel. +49 (0)221 - 931245-0 Fax +49 (0)221 - 931245-33</p> <p><b>Sampling by*</b> (name, company, phone) Le Huu Nghi - Tel: +84 62924344 International Environment Co.Ltd</p> <p><b>Sampling location*</b> 35/10, 48 Street, 14 Ward, Go Vap District, Ho Chi Minh City, Vietnam</p> <p><b>Product type</b> Mattress core (e.g. parquet, floor covering)</p> <p><b>Sample/ Batch*</b> 100701006017</p> <p><b>Production date of batch*</b> 01/07/2024</p> <p><b>Sampling date*</b> 03/07/2024</p> <p><b>Storage conditions before sampling</b> <input checked="" type="checkbox"/> open <input type="checkbox"/> packaged</p> <p><b>Packaging material</b></p>
--	---



**Additional information, if applicable / Special issues**  
 Uncertainties, questions, possible negative effects through emissions at place of sampling - e.g. contaminations during production/storage

**Validation\***  
 By signing the accuracy of the above-mentioned statements (**sampling**) is affirmed.

**Date**  
 (dd/mm/yyyy) 03/07/2024

**Signature**  
  
 GIÁM ĐỐC  
 Le Huu Nghi



eco-INSTITUT Germany GmbH / Schanzenstrasse 6-20 / Carlswerk 1.19 / D-51063 Köln / Germany  
 Tel. +49 221.931245-0 / Fax +49 221.931245-33 / eco-institut.de / Geschäftsführer: Dr. Frank Kuebart, Daniel Tigges  
 HRB 17917 / USt-ID: DE 122653308 / Volksbank Rhein-Erft-Köln eG, IBAN: DE60370623651701900010, BIC: GENODE33HAN



## Sampling Sheet

Please fill in all fields. If the fields marked \* are not filled in, the test piece cannot be accepted for laboratory testing.

# 59327-002

Please take one sampling sheet for each sample! The sampling instruction must be strictly maintained!

<b>Order by*</b>		<b>Testing laboratory</b>	eco-INSTITUT Germany GmbH Schanzenstr. 6-20, Carlswerk 1.19 D - 51063 Köln Tel. +49 (0)221 - 931245-0 Fax +49 (0)221 - 931245-33
<input checked="" type="checkbox"/> <b>Name of production company</b>	Lien A Co., Ltd. 55/1A Khuong Viet Street, Phu Trung Ward, Tan Phu District, Ho Chi Minh Citu, Vietnam	<b>Sampling by*</b> (name, company, phone)	Lo Huu Nghi - Tel: +84 62924344 International Environment Co.Ltd
<b>Name of distribution</b> (if different from production)		<b>Sampling location*</b>	35/10, 48 Street, 14 Ward, Go Vap District, Ho Chi Minh City, Vietnam
<b>Name of test sample/ item*</b>	C. Fusion Latex	<b>Product type</b>	Pillow (e.g. parquet, floor covering)
<b>Article number</b>		<b>Sample/ Batch*</b>	10070155
<b>Model / Program / Series</b>	Oval Pillow	<b>Production date of batch*</b>	01/07/2024
<b>Sample taken from</b>	<input checked="" type="checkbox"/> current production <input type="checkbox"/> storage <input type="checkbox"/> other	<b>Sampling date*</b>	03/07/2024
<b>Storage location</b>		<b>Storage conditions before sampling</b>	<input checked="" type="checkbox"/> open <input type="checkbox"/> packaged
		<b>Packaging material</b>	



**Additional information, if applicable / Special issues**  
 Uncertainties, questions, possible negative effects through emissions at place of sampling - e.g. contaminations during production/storage

**Validation\***  
 By signing the accuracy of the above-mentioned statements (**sampling**) is affirmed.

**Date**  
 (dd/mm/yyyy) 03/07/2024

**Signature**  
  
 GIÁM ĐỐC  
 Lê Hữu Nghi

eco-INSTITUT Germany GmbH / Schanzenstrasse 6-20 / Carlswerk 1.19 / D-51063 Köln / Germany  
 Tel. +49 221.931245-0 / Fax +49 221.931245-33 / eco-institut.de / Geschäftsführer: Dr. Frank Kuebart, Daniel Tigges  
 HRB 17917 / USt-ID: DE 122653308 / Volksbank Rhein-Erft-Köln eG, IBAN: DE60370623651701900010, BIC: GENODE33HAN30

## List of calibrated Volatile Organic Compounds (VOC)

### Aromatic hydrocarbons (31)

Benzene<sup>4</sup>  
1,2,3-Trimethylbenzene  
1,2,4-Trimethylbenzene  
1,3,5-Trimethylbenzene  
1-Isopropyl-2-methylbenzene  
1-Isopropyl-4-methylbenzene  
1,2,4,5-Tetramethylbenzene  
Ethylbenzene  
n-Propylbenzene  
Isopropylbenzene (Cumene)<sup>4</sup>  
1,3-Diisopropylbenzene  
1,4-Diisopropylbenzene  
n-Butylbenzene  
1-Propenylbenzene (beta-Methylstyrene)  
Toluene  
2-Ethyltoluene  
Vinyltoluene  
o-Xylene  
m-/p-Xylene  
Styrene  
Phenylacetylene  
2-Phenylpropene (alpha-Methylstyrene)  
4-Phenylcyclohexene  
1-Phenylcyclohexane  
1-Phenyldecane<sup>2</sup>  
1-Phenylundecane<sup>2</sup>  
Indene  
Naphthalene  
1-Methylnaphthalene  
2-Methylnaphthalene  
1,4-Dimethylnaphthalene

### Aliphatic hydrocarbons (23)

2-Methylpentane<sup>1</sup>  
3-Methylpentane<sup>1</sup>  
Methylcyclopentane  
n-Hexane  
Cyclohexane  
Methylcyclohexane  
1,4-Dimethylcyclohexane  
n-Heptane  
2,2,4,4,6,6-Pentamethylheptane  
n-Octane  
n-Nonane  
n-Decane  
n-Undecane  
n-Dodecane  
n-Tridecane  
n-Tetradecane  
n-Pentadecane  
n-Hexadecane  
Decahydronaphthalene  
1-Octene  
1-Decene  
1-Dodecene  
4-Vinylcyclohexene

### Terpenes (12)

delta-3-Carene  
alpha-Pinene  
beta-Pinene  
alpha-Terpinene  
Longipinene  
Limonene  
Longifolene  
Isolongifolene  
beta-Caryophyllene  
alpha-Phellandrene  
Myrcene  
Camphene

### Aliphatic alcohols and ether (18)

Ethanol<sup>1</sup>  
1-Propanol<sup>1</sup>  
2-Propanol<sup>1</sup>  
2-Methyl-1-propanol  
1-Butanol  
tert-Butanol  
1-Pentanol  
1-Hexanol  
Cyclohexanol  
2-Ethyl-1-hexanol  
1-Heptanol  
1-Octanol  
1-Nonanol  
1-Decanol  
1,4-Cyclohexandimethanol  
4-Hydroxy-4-methyl-pentan-2-one  
(Diacetone alcohol)  
Methyl-tert-butyl ether (MTBE)<sup>1</sup>  
Tetrahydrofuran (THF)

### Aromatic alcohols (phenoles) (8)

Furfuryl alcohol  
Benzyl alcohol  
Phenol  
2-Phenylphenol (oPP)  
BHT (2,6-Di-tert-butyl-4-methylphenol)  
o-Cresol  
m-/p-Cresol  
4-Chloro-3-methylphenol (Chlorocresol)

### Glycols, Glycol ether, Glycol ester (49)

Ethyleneglycol (Ethan-1,2-diol)  
Propylenglycol (Propane-1,2-diol)  
Diethylene glycol  
Dipropylene glycol  
Neopentyl glycol  
Hexyleneglycol  
Ethylidiglycol  
Ethylene glycol monobutyl ether  
Diethylene glycol methyl ether  
Diethylene glycol monobutyl ether  
Diethylene glycol phenyl ether  
Dipropylene glycol-dimethyl ether

Dipropylene glycol mono-n-butyl ether  
Dipropylene glycol mono-tert-butyl ether  
Dipropylene glycol monomethyl ether  
Dipropylene glycol mono-n-propyl ether  
Tripropylene glycol monomethyl ether  
Triethylene glycol dimethyl ether  
1,2-Propylene glycol dimethyl ether  
1,2-Propylene glycol-n-propyl ether  
1,2-Propylene glycol-n-butyl ether  
Butyl glycolate  
2-Methoxyethanol  
2-Ethoxyethanol  
2-Methylethoxyethanol  
2-Propoxyethanol  
2-Hexoxyethanol  
2-(2-Hexoxyethoxy)ethanol  
2-Phenoxyethanol  
1-Methoxy-2-propanol  
2-Methoxy-1-propanol  
1-Ethoxy-2-propanol  
1-tert-Butoxy-2-propanol  
3-Methoxy-1-butanol  
1,4-Butanediol  
1,2-Dimethoxyethane  
1,2-Diethoxyethane  
1-Methoxy-2-(2-methoxy-ethoxy)ethane  
Ethylene carbonate  
Propylene carbonate  
2-Methoxy-1-propyl acetate  
Diethylene glycol monomethyl ether acetate  
2-Methoxyethyl acetate  
2-Ethoxyethyl acetate  
2-Butoxy ethyl acetate  
Dipropylene glycol monomethyl ether acetate  
Propylene glycol diacetate  
Texanol  
TXIB (Texanol isobutyrate)

### Aldehydes (26)

Formaldehyde<sup>1,3,4</sup>  
Acetaldehyde<sup>1,3,4</sup>  
Propanal<sup>1,3</sup>  
Butanal<sup>1,3</sup>  
3-Methyl-1-butanal  
Pentanal  
Hexanal  
2-Ethylhexanal  
Heptanal  
Octanal  
Nonanal  
Decanal  
Propenal (Acrolein)<sup>1</sup>  
Isobutanal (Methacrolein)<sup>3</sup>  
2-Butenal  
2-Pentenal<sup>3</sup>  
2-Hexenal  
2-Heptenal  
2-Octenal



2-Nonenal  
2-Decenal  
2-Undecenal  
Ethanedial (Glyoxal)<sup>1,3</sup>  
Glutaraldehyde  
Furfural  
Benzaldehyde

#### Ketones (15)

Acetone<sup>1,3</sup>  
1-Hydroxyacetone  
Ethylmethylketone<sup>3</sup>  
Methylisobutylketone  
3-Methyl-2-butanone  
Cyclopentanone  
2-Methylcyclopentanone  
Cyclohexanone  
2-Methylcyclohexanone  
2-Hexanone  
2-Heptanone  
Acetophenone  
Isophorone  
Benzophenone<sup>4</sup>  
4-Methylbenzophenone<sup>2</sup>

#### Acids (11)

Acetic acid  
Propionic acid  
Pivalic acid  
Butyric acid  
Isobutyric acid  
n-Valeric acid  
n-Caproic acid  
2-Ethylhexanoic acid  
n-Heptanoic acid  
n-Octanoic acid  
Neodecanoic acid

#### Esters and Lactones (33)

Methyl acetate<sup>1</sup>  
Ethyl acetate<sup>1</sup>  
Vinyl acetate<sup>1</sup>  
Propyl acetate  
Isopropyl acetate  
2-Methoxy-1-methylethyl acetate  
n-Butyl acetate  
Isobutylacetate  
2-Ethylhexyl acetate  
n-Butyl formate

Methyl acrylate  
Methyl methacrylate  
Butyl methacrylate  
Ethyl acrylate  
n-Butyl acrylate  
2-Ethylhexyl acrylate  
2-Ethylhexyl methacrylate  
Hexanediol diacrylate  
Dipropylene glycol diacrylate  
Dimethyl succinate  
Dimethyl glutarate  
Dimethyl adipate  
Dibutyl fumarate  
Dibutyl maleate  
Diisobutyl succinate  
Diisobutyl glutarate  
Butyrolactone  
Dimethyl phthalate  
Diethyl phthalate<sup>2</sup>  
Dipropyl phthalate<sup>2</sup>  
Dibutyl phthalate<sup>2</sup>  
Diisobutyl phthalate<sup>2</sup>  
(5-Ethyl-1,3-dioxan-5-yl)methyl acrylate

#### Chlorinated hydrocarbons (18)

Dichloromethane<sup>1</sup>  
Trichloromethane (Chloroform)<sup>4</sup>  
Tetrachloromethane  
1,2-Dichloroethane<sup>4</sup>  
1,1,1-Trichloroethane  
2-Chloropropane  
1,2,3-Trichloropropane<sup>4</sup>  
Trichloroethene<sup>4</sup>  
Tetrachloroethene  
trans-1,3-Dichloropropene<sup>4</sup>  
cis-1,3-Dichloropropene<sup>4</sup>  
Chloroprene<sup>4</sup>  
1,3-Dichloro-2-propanol<sup>4</sup>  
Chlorobenzene  
1,4-Dichlorobenzene  
alpha-Chlorotoluene<sup>4</sup>  
alpha,alpha,alpha-Trichlorotoluene<sup>4</sup>  
1,1-Dichloroethene<sup>1</sup>

#### Cyclic siloxanes (5)

Hexamethylcyclotrisiloxane (D3)  
Octamethylcyclotetrasiloxane (D4)  
Decamethylcyclopentasiloxane (D5)  
Dodecamethylcyclohexasiloxane (D6)  
Tetradecamethylcycloheptasiloxane (D7)

#### Others (42)

1,4-Dioxane<sup>4</sup>  
1,2-Dibromoethane<sup>4</sup>  
2-Nitropropane<sup>4</sup>  
2,3-Dinitrotoluene<sup>4</sup>  
2,4-Dinitrotoluene<sup>4</sup>  
2,6-Dinitrotoluene<sup>4</sup>  
3,4-Dinitrotoluene<sup>2,4</sup>  
o-Anisidine<sup>4</sup>  
o-Toluidine<sup>4</sup>  
4-Chloro-o-toluidine<sup>4</sup>  
5-Nitro-o-toluidine<sup>2</sup>  
Acrylonitrile<sup>1,4</sup>  
2,2'-Azobisisobutyronitrile  
Tetramethylsuccinonitrile  
Azobenzene<sup>2,4</sup>  
Caprolactam  
Furan<sup>1,4</sup>  
2-Methylfuran  
2-Pentylfuran  
Methenamine  
Triethylamine  
2-Butanoxime<sup>4</sup>  
Triethyl phosphate  
Tributyl phosphate<sup>2</sup>  
5-Chloro-2-methyl-4-isothiazolin-3-one (CIT)  
2-Methyl-4-isothiazolin-3-one (MIT)  
2-n-Octyl-4-isothiazolin-3-one (OIT)  
Formamide  
Dimethylformamide (DMF)  
Acetamide  
N-Nitrosopyrrolidine<sup>4</sup>  
N-Methyl-2-pyrrolidone  
N-Ethyl-2-pyrrolidone  
N-Butyl-2-pyrrolidone  
Aniline<sup>5</sup>  
4-Chloroaniline<sup>4</sup>  
2-Nitroanisole<sup>4</sup>  
Cyclohexyl isocyanate  
p-Cresidine<sup>4</sup>  
Diethyl sulfate<sup>4</sup>  
Epichlorohydrin<sup>4</sup>  
5-Ethyl-1,3-dioxan-5-methanol

1 VVOC

2 SVOC

3 Analysis acc. to DIN ISO 16000-3:2023-12 (DNPH)

4 Carcinogens, category 1A and 1B according to Regulation (EC) No 1272/2008 and TRGS 905

5 When analysing with TD-GC-MS, aniline can occur as a thermal decomposition product of other substances (e.g. 1,3-Diphenylguanidine).  
A cold analytical method is recommended to confirm the result.

(Status: August 2024)

## Definition of terms

CAS No. (Chemical Abstracts Service)	International designation standard for chemical substances
CMR	VOCs, VVOCs and SVOCs classified as carcinogenic, mutagenic or toxic for reproduction according to Regulation (EC) No. 1272/2008, TRGS 905, IARC list and DFG (MAK list)
Limit of quantification (LOQ)	Lower limit of quantification in the analytical method within the defined measurement uncertainty
NIK / LCI	Lowest concentration of interest; substance-specific value for health assessment of emissions from products, indicated in $\mu\text{g}/\text{m}^3$
RT (retention time)	Total time required for an analyte to pass the column (time between injection and detection of the analyte)
R value	Sum of quotients of concentration and LCI value for all substances for which a LCI value is derived
R value according to AgBB	R-value for all substances $\geq 5 \mu\text{g}/\text{m}^3$ with LCI value, calculated according to the LCI list of the AgBB scheme
R-value according to Belgian regulation	R-value for all substances $\geq 5 \mu\text{g}/\text{m}^3$ with LCI-value, calculated according to the LCI-list of the Belgian regulation
R value according to eco-INSTITUT-Label	R-value for all substances $\geq 1 \mu\text{g}/\text{m}^3$ with LCI value, calculated according to the LCI list of the AgBB scheme
R value according to EU-LCI	R-value for all substances $\geq 5 \mu\text{g}/\text{m}^3$ with EU-LCI value, calculated according to the EU-LCI list of the European Commission
SER	Specific emission rate (see "Explanation of Specific Emission Rate SER")
SVOC (semi volatile organic compound)	Organic compound eluting in the retention range $> C_{16}$ (n-hexadecane) to $C_{22}$ (docosane)
Toluene equivalent	Concentration of a substance quantified by the TIC response factor of toluene (calculation of the concentration by comparing the integral of the substance with the integral of toluene)
TSVOC	Sum of the concentrations of all identified and unidentified semi volatile organic compounds eluting in the retention range $> C_{16}$ (n-hexadecane) to $C_{22}$ (docosane)
TSVOC according to DIN EN 16516	Sum of all SVOC $\geq 5 \mu\text{g}/\text{m}^3$ (as toluene equivalent)
TSVOC with LCI according to AgBB	Sum of all SVOC with LCI $\geq 5 \mu\text{g}/\text{m}^3$ (quantified substance-specific)
TSVOC with LCI according to eco-INSTITUT-Label	Sum of all SVOC with LCI $\geq 1 \mu\text{g}/\text{m}^3$ (quantified substance-specific)
TSVOC without LCI according to AgBB	Sum of all SVOC without LCI $\geq 5 \mu\text{g}/\text{m}^3$ (as toluene equivalent)
TSVOC without LCI according to eco-INSTITUT label	Sum of all calibrated SVOC without LCI $\geq 1 \mu\text{g}/\text{m}^3$ (quantified substance-specific) and all non-calibrated SVOC without LCI $\geq 1 \mu\text{g}/\text{m}^3$ (as toluene equivalent)
TVOC	Sum of the concentrations of all identified and unidentified volatile organic compounds eluting in the retention range from $C_6$ (n-hexane) to $C_{16}$ (n-hexadecane)

TVOC according to DIN EN 16516	Sum of all VOC $\geq 5 \mu\text{g}/\text{m}^3$ in the retention range $C_6$ to $C_{16}$ , calculated as toluene equivalent (used i.a. for M1)
TVOC according to AgBB	Sum of all VOCs with LCI $\geq 5 \mu\text{g}/\text{m}^3$ (quantified substance-specific) and all VOCs without LCI $\geq 5 \mu\text{g}/\text{m}^3$ (as toluene equivalent) (used i.a. for the Blue Angel)
TVOC according to eco-INSTITUT-Label	Sum of all calibrated VOC $\geq 1 \mu\text{g}/\text{m}^3$ (quantified substance-specific) and all non-calibrated VOC $\geq 1 \mu\text{g}/\text{m}^3$ (as toluene equivalent) (used i.a. for natureplus)
TVOC according to ISO 16000-6	Total area of the chromatogram in the retention range $C_6 - C_{16}$ as toluene equivalent according to DIN ISO 16000-6, Annex A.1 item 3 (used i.a. for CDPH, BIFMA and the French VOC regulation)
TVOC without LCI according to AgBB	Sum of all VOCs without LCI $\geq 5 \mu\text{g}/\text{m}^3$ as toluene equivalent
TVOC without LCI according to eco-INSTITUT-Label	Sum of all calibrated VOCs without LCI $\geq 1 \mu\text{g}/\text{m}^3$ (quantified substance-specific) and all non-calibrated VOCs without LCI $\geq 1 \mu\text{g}/\text{m}^3$ (as toluene equivalent)
TVVOC	Sum of the concentrations of all identified and unidentified very volatile organic compounds eluting in the retention range $< C_6$ (n-hexane)
TVVOC according to AgBB	Sum of all VVOC with LCI $\geq 5 \mu\text{g}/\text{m}^3$ (quantified substance-specific) and all VVOC without LCI $\geq 5 \mu\text{g}/\text{m}^3$ (as toluene equivalent)
TVVOC according to eco-INSTITUT-Label	Sum of all calibrated VVOC $\geq 1 \mu\text{g}/\text{m}^3$ (substance-specific quantified) and all non-calibrated VVOC $\geq 1 \mu\text{g}/\text{m}^3$ (as toluene equivalent)
VOC (volatile organic compound)	Organic compound eluting in the retention range from $C_6$ (n-hexane) to $C_{16}$ (n-hexadecane)
VVOC (very volatile organic compound)	Organic compound eluting in the retention range $< C_6$ (n-hexane)

## Commentary on emission analysis

### Test method

Measurement of the volatile organic compounds takes place in the test chamber in conditions similar to those applying in practice. Standardised test conditions are defined for the test chamber regarding loading, air exchange, relative humidity, temperature, and incoming air, based on the type of test specimen and the required guideline. These conditions and the underlying standards are to be found in the section on test methods in the laboratory report.

Air samples are taken from the test chamber at defined points in time during the continuously running test. To this end, approximately 5 L of air are collected from the test chamber at an air flow rate of 100 mL/min on Tenax and approx. 100 L at an air flow rate of 0.8 L/min on silica gel coated with DNPH (2,4-dinitrophenylhydrazine).

After thermal desorption, the substances adsorbed on Tenax are analysed using gas chromatographic separation and mass spectrometric determination. The gas chromatographic separation is performed with a slightly polar capillary column of 60 m in length.

The substances derivatised with DNPH for the determination of formaldehyde and other short-chain carbonyl compounds (C<sub>1</sub> - C<sub>6</sub>) are analysed using high-performance liquid chromatography (HPLC).

Over 200 compounds, including volatile organic compounds (C<sub>6</sub> - C<sub>16</sub>), semi-volatile organic compounds (C<sub>16</sub> - C<sub>22</sub>) and – insofar as possible with this method – also very volatile organic compounds (less than C<sub>6</sub>) are determined and quantified individually.

All other substances – insofar as possible – are identified through comparison with a library of spectra. The quantification of these substances and non-identified substances is performed through a comparison of their signal area with the signal of toluene.

The determined substance concentrations are corrected using the recovery rate of the internal standard (toluene-d8). Identification and quantification of substances is carried out from a concentration (limit of quantification) of 1 µg per m<sup>3</sup> test chamber air or 2 µg/m<sup>3</sup> for DNPH-derivatised substances. In the case of highly loaded samples, the evaluation limit of non-calibrated substances is raised in some cases, as it is no longer possible to assign individual, small signals due to the large number of signals.

### Quality assurance

The eco-INSTITUT Germany GmbH is granted flexible scope of accreditation pursuant to DIN EN ISO/IEC 17025:2018-03. The accreditation covers the analytical determination of all volatile organic compounds, including the test chamber method.

In each analysis the analytical system is checked using an external standard based on the specifications in standard DIN EN 16516:2020-10. The stability of the analytical systems is documented based on the test standard using control charts.

Laboratory performance is assessed at least once a year in inter-laboratory comparisons by comparing the results with those obtained by other laboratories for identical samples.

A blank is run prior to introducing the test specimen into the test chamber to check for the possible presence of volatile organic compounds.

The expanded measurement uncertainty U for the analytical determination of all volatile organic compounds, including the test chamber method, is estimated to 41.7 %. The calculation is based on DIN ISO 11352:2013-03 (Nordtest).



## Explanation of Specific Emission Rate SER

Emission measurements are accomplished in test chambers under defined physical conditions (temperature, relative humidity, room loading, air change rate etc.).

Test chamber measurement results are directly comparable only if the investigations were accomplished under the same basic conditions.

If the differences of the physical conditions refer only to the change of air rate and/or the loading, the "SER" or "specific emission rate" can be used for comparability of the measurement results. The SER indicates how many volatile organic compounds (VOC) are released by the sample for each material unit and hour (h).

The SER can be calculated using the formula below for each proven individual component of the VOC from the data in the test report.

As material units the following are applicable:

l = unit of length (m)	relation between emission and length
a = unit area (m <sup>2</sup> )	relation between emission and surface
v = unit volume (m <sup>3</sup> )	relation between emission and volume
u = piece unit (unit = piece)	relation between emission and complete unit

From this the different dimensions for SER result:

length-specific	SER <sub>l</sub>	in µg/(m·h)
surface-specific	SER <sub>a</sub>	in µg/(m <sup>2</sup> ·h)
volume-specific	SER <sub>v</sub>	in µg/(m <sup>3</sup> ·h)
unit-specific	SER <sub>u</sub>	in µg/(u·h)

SER thus represents a product specific rate, which describes the mass of the volatile organic compound, which is emitted by the product per time unit at a certain time after beginning of the examination.

$$\text{SER} = q \cdot c$$

- q      specific air flow rate (quotient from change of air rate and loading)  
c      concentration of the measured substance(s)

The result can be indicated in milligrams (mg) in place of micro grams (µg), whereby 1 mg = 1000 µg.